Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

SKU: 9781138490499-SOLUTIONS

Chapter 2

Vectors and tensors

2.1 Exercise

1. Prove the following identity equations using the index notation:

$$\mathbf{a.}\left(\mathbf{bc}\right)=\left(\mathbf{ab}\right)\mathbf{.c}$$

$$\mathbf{a}\left(\mathbf{bc}\right)=\left(\mathbf{a.c}\right)\mathbf{b}-\left(\mathbf{a.b}\right)\mathbf{c}$$

$$\left(\mathbf{ab}\right)\mathbf{.}\left(\mathbf{cd}\right)=\mathbf{a.}\left[\mathbf{b}\left(\mathbf{cd}\right)\right]$$

Proof:

(1)$\mathbf{a}\cdot(\mathbf{b}\times\mathbf{c})$=$a_i(\varepsilon_{ijk}b_jc_k)=(\varepsilon_{ijk}a_ib_j)c_k$= $(\mathbf{a}\times\mathbf{b})\cdot\mathbf{c}$

(2)$\mathbf{a}\times(\mathbf{b}\times\mathbf{c})$=$\varepsilon_{ijk}a_j(\varepsilon_{klm}b_lc_m)=(\varepsilon_{ijk}\varepsilon_{lmk})a_jb_lc_m$= $(\delta_{ij}\delta_{jm}-\delta_{im}\delta_{jl})a_jb_lc_m$

$=a_jb_ic_j-a_jb_jc_i$=$(a_jc_j)b_j-(a_jb_j)c_i$=$(\mathbf{a}\cdot\mathbf{c})\mathbf{b}-(\mathbf{a}\cdot\mathbf{b})\mathbf{c}$

(3)$(\mathbf{a}\times\mathbf{b})\cdot(\mathbf{c}\times\mathbf{d})$=$(\varepsilon_{ijk}a_ib_j)(\varepsilon_{klm}c_ld_m)$=$a_i(\varepsilon_{ijk}b_j(\varepsilon_{lmk}c_ld_m)$=$\mathbf{a}\cdot[\mathbf{b}\times(\mathbf{c}\times\mathbf{d})]$

2. For a rotational matrix $\mathbf{Q}$ between two Cartesian coordinates $\mathbf{x}$ and $\mathbf{x}$' with a common origin, say $Q_{ij}=cos(x_i,x_j^{'})$. The angular relationship between any two Cartesian reference frames $\mathbf{x}$ and $\mathbf{x}$' can be represented in terms of three Euler angles(ϕ,θ,ψ) as follows: a) the first rotation is by an angle ϕ about the x_3 axis, b) the second rotation is by an angle $\theta\in(0,\pi)$about the $x_1$axis, and c) the third rotation is by an angle ψ about the the x_3 axis again. Then the transformation matrix can be written as:

$$\mathbf{Q}=\begin{bmatrix}\cos\psi\cos\phi-\cos\theta\sin\psi\sin\phi & \cos\psi\sin\phi+\cos\theta\sin\psi\cos\phi & \sin\psi\sin\theta\\ -\sin\psi\cos\phi-\cos\theta\cos\psi\sin\phi & -\sin\psi\sin\phi+\cos\theta\cos\psi\cos\phi & \cos\psi\sin\theta\\ \sin\theta\sin\phi & -\sin\theta\cos\phi & \cos\theta\end{bmatrix}.$$

Prove

$$Q_{ik}Q_{jk}=\delta_{ij}.$$

Proof:

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

We calculate this one by one

$$Q_{1k}Q_{1k}$$

$$=(\cos\psi\cos\phi-\cos\theta\sin\psi\sin\phi)^2+(\cos\psi\sin\phi+\cos\theta\sin\psi\cos\phi)^2+(\sin\psi\sin\theta)^2$$

$$=\cos^2\psi\cos^2\phi-2\cos\psi\cos\phi\cos\theta\sin\psi\sin\phi+\cos^2\theta\sin^2\psi\cos^2\phi$$

$$+\cos^2\psi\sin^2\phi+2\cos\theta\sin\psi\cos\phi+\cos^2\theta\sin^2\psi\cos^2\phi+\sin^2\psi\sin^2\theta$$

$$=\left(\cos^2\psi\cos^2\phi+\cos^2\psi\sin^2\phi\right)$$

$$+\left(\cos^2\theta\sin^2\psi\cos^2\phi+\cos^2\theta\sin^2\psi\cos^2\phi\right)+\sin^2\psi\sin^2\theta$$

$$=\cos^2\psi+\cos^2\theta\sin^2\psi+\sin^2\psi\sin^2\theta$$

$$=1$$

$$Q_{1k}Q_{2k}$$

$$=(\cos\psi\cos\phi-\cos\theta\sin\psi\sin\phi)\,(-\sin\psi\cos\phi-\cos\theta\cos\psi\sin\phi)$$

$$+(\cos\psi\sin\phi+\cos\theta\sin\psi\cos\phi)\,(-\sin\psi\sin\phi+\cos\theta\cos\psi\cos\phi)$$

$$+(\sin\psi\sin\theta)\,(\cos\psi\sin\theta)$$

$$=-\cos\psi\cos^2\phi\sin\psi-\cos^2\psi\cos\phi\cos\theta\sin\phi+\cos\theta\sin^2\psi\sin\phi\cos\phi+\cos^2\theta\sin\psi\sin^2\phi\cos\psi$$

$$-\cos\psi\sin^2\phi\sin\psi+\cos^2\psi\cos\phi\cos\theta\sin\phi-\cos\theta\sin^2\psi\sin\phi\cos\phi+\cos^2\theta\sin\psi\cos^2\phi\cos\psi$$

$$+\sin\psi\cos\psi\sin^2\theta$$

$$=-\left(\cos\psi\cos^2\phi\sin\psi+\cos\psi\sin^2\phi\sin\psi\right)$$

$$+\left(\cos^2\theta\sin\psi\sin^2\phi\cos\psi+\cos^2\theta\sin\psi\cos^2\phi\cos\psi\right)$$

$$+\sin\psi\cos\psi\sin^2\theta$$

$$=-\cos\psi\sin\psi+\cos^2\theta\sin\psi\cos\psi+\sin\psi\cos\psi\sin^2\theta$$

$$=0$$

$$Q_{1k}Q_{3k}$$

$$=(\cos\psi\cos\phi-\cos\theta\sin\psi\sin\phi)\,(\sin\theta\sin\phi)$$

$$+(\cos\psi\sin\phi+\cos\theta\sin\psi\cos\phi)\,(-\sin\theta\cos\phi)$$

$$+(\sin\psi\sin\theta)\cos\theta$$

$$=\cos\psi\cos\phi\sin\theta\sin\phi-\cos\theta\sin\psi\sin^2\phi\sin\theta$$

$$-\cos\psi\sin\phi\sin\theta\cos\phi-\cos\theta\sin\psi\cos^2\phi\sin\theta$$

$$+\sin\psi\sin\theta\cos\theta$$

$$=-\cos\theta\sin\psi\left(\sin^2\phi+\cos^2\phi\right)\sin\theta+\sin\psi\sin\theta\cos\theta$$

$$=0$$

$$Q_{2k}Q_{2k}$$

$$=(-\sin\psi\cos\phi-\cos\theta\cos\psi\sin\phi)\,(-\sin\psi\sin\phi-\cos\theta\cos\psi\sin\phi)$$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

$$
\begin{aligned}
&+(\sin\psi\sin\phi+\cos\theta\cos\psi\cos\phi)\,(-\sin\psi\sin\phi+\cos\theta\cos\psi\cos\phi)\\
&+(\cos\psi\sin\theta)\,(\cos\psi\sin\theta)\\
&=\sin^2\psi\cos^2\phi+2\sin\psi\cos\phi\cos\theta\cos\psi\sin\phi+\cos^2\theta\cos^2\psi\sin^2\phi\\
&+\sin^2\psi\sin^2\phi-2\sin\psi\sin\phi\cos\theta\cos\psi\cos\phi+\cos^2\theta\cos^2\psi\cos^2\phi\\
&+\cos^2\psi\sin^2\theta\\
&=\left(\sin^2\psi\cos^2\phi+\sin^2\psi\sin^2\phi\right)\\
&+\left(\cos^2\theta\cos^2\psi\sin^2\phi+\cos^2\theta\cos^2\psi\cos^2\phi\right)\\
&+\cos^2\psi\sin^2\theta\\
&=\sin^2\psi+\cos^2\theta\cos^2\psi+\cos^2\psi\sin^2\theta\\
&=1
\end{aligned}
$$

$$
\begin{aligned}
&Q_{2k}Q_{3k}\\
&=(-\sin\psi\cos\phi-\cos\theta\cos\psi\sin\phi)\,(\sin\theta\sin\phi)\\
&+(-\sin\psi\sin\phi+\cos\theta\cos\psi\cos\phi)\,(-\sin\theta\cos\phi)\\
&+(\cos\psi\sin\theta)\,(\cos\theta)\\
&=-\sin\psi\cos\phi\sin\theta\sin\phi-\cos\theta\cos\psi\sin\phi\sin\theta\sin\phi\\
&+\sin\psi\sin\phi\sin\theta\cos\phi-\cos\theta\cos\psi\cos\phi\sin\theta\cos\phi\\
&+\cos\psi\sin\theta\cos\theta\\
&=-\cos\theta\cos\psi\left(\sin^2\phi+\cos^2\phi\right)\sin\theta+\cos\psi\sin\theta\cos\theta\\
&=0
\end{aligned}
$$

$$
\begin{aligned}
&Q_{3k}Q_{3k}\\
&=(\sin\theta\sin\phi)^2+(-\sin\theta\cos\phi)^2+\cos^2\theta\\
&=\sin^2\theta\left(\sin^2\phi+\cos^2\phi\right)+\cos^2\theta\\
&=1
\end{aligned}
$$

And for symmetry

$Q_{2k}Q_{1k}=Q_{1k}Q_{2k}=0$

$Q_{3k}Q_{1k}=Q_{1k}Q_{3k}=0$

$Q_{3k}Q_{2k}=Q_{2k}Q_{3k}=0$

So

$Q_{ik}Q_{jk}=\delta_{ij}$

3. Prove the following tensors are isotropic for the corresponding tensor ranks:

$$A_{ij}=k\delta_{ij};\ A_{ijk}=ke_{ijk};\ A_{ijkl}=\alpha\delta_{ij}\delta_{kl}+\beta\delta_{ik}\delta_{jl}+\gamma\delta_{il}\delta_{jk};$$

Proof:

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

1. We need to point out that the transformation matrix $\mathbf{Q}$, it satisfies

$Q_{mi}Q_{ni} = \delta_{mn}$

For $\lambda\delta_{ij}$,under the transformation matrix Q,it becomes

$Q_{mi}Q_{nj}\lambda\delta_{ij} = \lambda Q_{mi}Q_{ni} = \lambda\delta_{mn} = \lambda\delta_{ij}$

Since $\mathbf{Q}$ is transformation matrix, it satisfies $Q_{mi}Q_{ni} = \delta_{mn}$

2. For $A_{ijk} = \lambda e_{ijk}$ under a transformation, we can write

$A'_{lmn} = \lambda Q_{li}Q_{mj}Q_{nk}e_{ijk}$

Considering $e_{ijk} = (\mathbf{e}_i \times \mathbf{e}_j) \cdot \mathbf{e}_k$, we can write

$A'_{lmn} = \lambda Q_{li}Q_{mj}Q_{nk} (\mathbf{e}_i \times \mathbf{e}_j) \cdot \mathbf{e}_k$

$= \lambda (Q_{li}\mathbf{e}_i \times Q_{mj}\mathbf{e}_j) \cdot Q_{nk}\mathbf{e}_k$

$= \lambda \left(\mathbf{e}'_l \times \mathbf{e}'_m\right) \cdot \mathbf{e}'_n$

Considering the propoerties of the base vector, $\left(\mathbf{e}'_l \times \mathbf{e}'_m\right) \cdot \mathbf{e}'_n = (\mathbf{e}_l \times \mathbf{e}_m) \cdot \mathbf{e}_n$ as the volume of the cubes of the vectors, we can write

$A'_{lmn} = \lambda \left(\mathbf{e}'_l \times \mathbf{e}'_m\right) \cdot \mathbf{e}'_n = \lambda (\mathbf{e}_l \times \mathbf{e}_m) \cdot \mathbf{e}_n = A_{lmn}$

So it is isotropic

3. For forth rank tensor $A_{ijkl} = \alpha\delta_{ij}\delta_{kl} + \beta\delta_{ik}\delta_{jl} + \gamma\delta_{il}\delta_{jk}$

$A'_{mnst} = Q_{mi}Q_{ni}Q_{sk}Q_{tk} (\alpha\delta_{ij}\delta_{kl} + \beta\delta_{ik}\delta_{jl} + \gamma\delta_{il}\delta_{jk})$

$= \alpha Q_{mi}Q_{ni}Q_{sk}Q_{tk} + \beta Q_{mi}Q_{nj}Q_{si}Q_{tj} + \gamma Q_{mi}Q_{nj}Q_{sj}Q_{ti}$

$= \alpha (Q_{mi}Q_{ni}) (Q_{sk}Q_{tk}) + \beta (Q_{mi}Q_{si}) (Q_{nj}Q_{tj}) + \gamma (Q_{mi}Q_{ti}) (Q_{bj}Q_{sj})$

$= \alpha\delta_{mn}\delta_{st} + \beta\delta_{mst}\delta_{nt} + \gamma\delta_{mt}\delta_{ns}$

$= A_{mnst}$

So it is isotropic

4. Consider vectors $\mathbf{a} = (1, 2, 3)$ and $\mathbf{b} = (3, 2, 1)$. Determine the following quantities:

$$\mathbf{a} \cdot \mathbf{b}, \mathbf{a} \times \mathbf{b}, \mathbf{a} \otimes \mathbf{b}.$$

Now if the coordinate is rotated along the axis x_3 at 30° counterclockwise, i.e. the $x_1 - x_2$ plane is rotated 30° counterclockwise and the x_3 axis remains the same, recalculate the above quantities in the new coordinate system.

Answer:

$\mathbf{a} \cdot \mathbf{b} = a_i b_i = 1 \times 3 + 2 \times 2 + 3 \times 1 = 10$

$\mathbf{a} \times \mathbf{b} = \varepsilon_{kij} a_i b_j = \begin{vmatrix} i & j & k \\ 1 & 2 & 3 \\ 3 & 2 & 1 \end{vmatrix} = (2 \times 1 - 3 \times 2)\, i + (3 \times 3 - 1 \times 1)\, j + (1 \times 2 - 2 \times 3)\, k =$

$(-4, 8, -4)$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

$$\mathbf{a}\otimes\mathbf{b}=a_ib_j=\begin{bmatrix}1\times3 & 1\times2 & 1\times1\\ 2\times3 & 2\times2 & 2\times1\\ 3\times3 & 3\times2 & 3\times1\end{bmatrix}=\begin{bmatrix}3 & 2 & 1\\ 6 & 4 & 2\\ 9 & 6 & 3\end{bmatrix}$$

Then we consider the condition of rotation,

The rotation matrix is

$$Q=\begin{bmatrix}\cos a & -\sin a & \\ \sin a & \cos a & \\ & & 1\end{bmatrix}=\begin{bmatrix}\cos 30 & -\sin 30 & \\ \sin 30 & \cos 30 & \\ & & 1\end{bmatrix}$$

After the rotation of the coordinate, the new quantities of the vectors would be

$$\mathbf{a}=(1,2,3)\begin{bmatrix}\cos 30 & -\sin 30 & \\ \sin 30 & \cos 30 & \\ & & 1\end{bmatrix}=\left(\tfrac{\sqrt{3}}{2}+1,-\tfrac{1}{2}+\sqrt{3},3\right)=(1.8660\ 1.2321\ 3.0000)$$

$$\mathbf{b}=(3,2,1)\begin{bmatrix}\cos 30 & -\sin 30 & \\ \sin 30 & \cos 30 & \\ & & 1\end{bmatrix}=\left(\tfrac{3\sqrt{3}}{2}+1,-\tfrac{3}{2}+\sqrt{3},1\right)=(3.5981\ 0.2321\ 1.0000)$$

Then

$$\mathbf{a}\cdot\mathbf{b}=a_ib_i=\left(\tfrac{\sqrt{3}}{2}+1\right)\times\left(\tfrac{3\sqrt{3}}{2}+1\right)+\left(-\tfrac{1}{2}+\sqrt{3}\right)\times\left(-\tfrac{3}{2}+\sqrt{3}\right)+3\times1$$

$$=\left(\tfrac{13}{4}+2\sqrt{3}\right)+\left(\tfrac{15}{4}-2\sqrt{3}\right)+3=10$$

$$\mathbf{a}\times\mathbf{b}=\varepsilon_{kij}a_ib_j=\begin{vmatrix} i & j & k\\ \frac{\sqrt{3}}{2}+1 & -\frac{1}{2}+\sqrt{3} & 3\\ \frac{3\sqrt{3}}{2}+1 & -\frac{3}{2}+\sqrt{3} & 1\end{vmatrix}$$

$$=\left[-\tfrac{1}{2}+\sqrt{3}-\left(-\tfrac{9}{2}+3\sqrt{3}\right)\right]i+\left[\tfrac{9\sqrt{3}}{2}+3-\left(\tfrac{\sqrt{3}}{2}+1\right)\right]j+\left[\tfrac{\sqrt{3}}{4}-\left(4+\tfrac{\sqrt{3}}{4}\right)\right]k$$

$$=\left(4-2\sqrt{3},4\sqrt{3}+2,-4\right)=(0.5359\ 8.9282\ -4.0000)$$

Note that this quantity of the vector is in the new coordinate system

$$\mathbf{a}\otimes\mathbf{b}=a_ib_j=\begin{bmatrix}\left(\frac{\sqrt{3}}{2}+1\right)\times\left(\frac{3\sqrt{3}}{2}+1\right) & \left(\frac{3\sqrt{3}}{2}+1\right)\times\left(-\frac{3}{2}+\sqrt{3}\right) & \left(\frac{\sqrt{3}}{2}+1\right)\times1\\ \left(-\frac{1}{2}+\sqrt{3}\right)\times\left(\frac{3\sqrt{3}}{2}+1\right) & \left(-\frac{1}{2}+\sqrt{3}\right)\times\left(-\frac{3}{2}+\sqrt{3}\right) & \left(-\frac{1}{2}+\sqrt{3}\right)\times1\\ 3\times\left(\frac{3\sqrt{3}}{2}+1\right) & 3\times\left(-\frac{3}{2}+\sqrt{3}\right) & 3\times1\end{bmatrix}$$

$$=\begin{bmatrix}\frac{13}{4}+2\sqrt{3} & \frac{\sqrt{3}}{4} & \frac{\sqrt{3}}{2}+1\\ 4+\frac{\sqrt{3}}{4} & \frac{15}{4}-2\sqrt{3} & -\frac{1}{2}+\sqrt{3}\\ \frac{9\sqrt{3}}{2}+3 & -\frac{9}{2}+3\sqrt{3} & 3\end{bmatrix}=\begin{bmatrix}6.7141 & 0.4330 & 1.8660\\ 4.4330 & 0.2859 & 1.2321\\ 10.7942 & 0.6962 & 3.0000\end{bmatrix}$$

Still in the new coordinate system.

5. An orthogonal material has the stiffness tensor given in form of $C_{ijkl}=C^1_{IK}\delta_{ij}\delta_{kl}+C^2_{IJ}\left(\delta_{ik}\delta_{jl}+\delta_{il}\delta_{jk}\right)$ with

$$\mathbf{C^1}=\begin{bmatrix}1 & 0.5 & 0.5\\ 0.5 & 1.5 & 0.75\\ 0.5 & 0.75 & 2\end{bmatrix};\ \mathbf{C^2}=\begin{bmatrix}0.5 & 0.25 & 0.25\\ 0.25 & 0.75 & 0.5\\ 0.25 & 0.5 & 1\end{bmatrix}.$$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

(a) Determine the components of the stiffness in form of a 6 by 6 matrix.

(b) Calculate the components of the compliance.

(c) Write the compliance tensor in the form of $D_{ijkl} = D^1_{IK}\delta_{ij}\delta_{kl} + D^2_{IJ}\left(\delta_{ik}\delta_{jl} + \delta_{il}\delta_{jk}\right)$. Determine D^1_{IK} and D^2_{IJ} in terms of C^1_{IK} and C^2_{IJ}. Check whether the calculation in (b) is consistent with the formulation.

Answer:

(a) The stiffness matrix transfers a strain tensor to a stress tensor as $\sigma_{ij} = C_{ijkl}\epsilon_{kl}$. Due to the symmetry of stress and strain, we can use a list of 6 components to represent the 3x3 tensor to save space in numerical programming as follows:

$$\begin{pmatrix} \sigma_{11} \\ \sigma_{22} \\ \sigma_{33} \\ \sigma_{23} \\ \sigma_{31} \\ \sigma_{12} \end{pmatrix} = \begin{bmatrix} C_{1111} & C_{1122} & C_{1133} & C_{1123} & C_{1131} & C_{1112} \\ C_{2211} & C_{2222} & C_{2233} & C_{2223} & C_{2231} & C_{2212} \\ C_{3311} & C_{3322} & C_{3333} & C_{3323} & C_{3331} & C_{3312} \\ C_{2311} & C_{2322} & C_{2333} & C_{2323} & C_{2331} & C_{2312} \\ C_{3111} & C_{3122} & C_{3133} & C_{3123} & C_{3131} & C_{3112} \\ C_{1211} & C_{1222} & C_{1233} & C_{1223} & C_{1231} & C_{1212} \end{bmatrix} \begin{pmatrix} \epsilon_{11} \\ \epsilon_{22} \\ \epsilon_{33} \\ 2\epsilon_{23} \\ 2\epsilon_{31} \\ 2\epsilon_{12} \end{pmatrix}$$

Notice that the strain list is the engineering strain instead of the tensorial strain, whose difference is in the shear strain components, i.e. $\gamma_{23} = 2\epsilon_{23}$, etc. but the normal strain s keep the same. If tensorial strain is used, the above relation becomes

$$\begin{pmatrix} \sigma_{11} \\ \sigma_{22} \\ \sigma_{33} \\ \sigma_{23} \\ \sigma_{31} \\ \sigma_{12} \end{pmatrix} = \begin{bmatrix} C_{1111} & C_{1122} & C_{1133} & 2C_{1123} & 2C_{1131} & 2C_{1112} \\ C_{2211} & C_{2222} & C_{2233} & 2C_{2223} & 2C_{2231} & 2C_{2212} \\ C_{3311} & C_{3322} & C_{3333} & 2C_{3323} & 2C_{3331} & 2C_{3312} \\ C_{2311} & C_{2322} & C_{2333} & 2C_{2323} & 2C_{2331} & 2C_{2312} \\ C_{3111} & C_{3122} & C_{3133} & 2C_{3123} & 2C_{3131} & 2C_{3112} \\ C_{1211} & C_{1222} & C_{1233} & 2C_{1223} & 2C_{1231} & 2C_{1212} \end{bmatrix} \begin{pmatrix} \epsilon_{11} \\ \epsilon_{22} \\ \epsilon_{33} \\ \epsilon_{23} \\ \epsilon_{31} \\ \epsilon_{12} \end{pmatrix}$$

where the symmetry of the stiffness tensor is lost. Therefore, we generally use the engineering strain in the 6-component notation. However, for orthotropic materials, because the components without symmetry are zero, this issue is not real. In the following, let us use engineering strain

$$C_{ijkl} = \begin{bmatrix} C_{1111} & C_{1122} & C_{1133} & C_{1123} & C_{1131} & C_{1112} \\ C_{2211} & C_{2222} & C_{2233} & C_{2223} & C_{2231} & C_{2212} \\ C_{3311} & C_{3322} & C_{3333} & C_{3323} & C_{3331} & C_{3312} \\ C_{2311} & C_{2322} & C_{2333} & C_{2323} & C_{2331} & C_{2312} \\ C_{3111} & C_{3122} & C_{3133} & C_{3123} & C_{3131} & C_{3112} \\ C_{1211} & C_{1222} & C_{1233} & C_{1223} & C_{1231} & C_{1212} \end{bmatrix}$$

$$= \begin{bmatrix} C^1_{11} + C^2_{11} \times 2 & C^1_{12} & C^1_{13} & 0 & 0 & 0 \\ C^1_{21} & C^1_{22} + C^2_{22} \times 2 & C^1_{32} & 0 & 0 & 0 \\ C^1_{31} & C^1_{32} & C^1_{33} + C^2_{33} \times 2 & 0 & 0 & 0 \\ 0 & 0 & 0 & C^2_{23} & 0 & 0 \\ 0 & 0 & 0 & 0 & C^2_{13} & 0 \\ 0 & 0 & 0 & 0 & 0 & C^2_{12} \end{bmatrix}$$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

$$= \begin{bmatrix} 1+0.5\times 2 & 0.5 & 0.5 & 0 & 0 & 0 \\ 0.5 & 1.5+0.75\times 2 & 0.75 & 0 & 0 & 0 \\ 0.5 & 0.75 & 1+0.5\times 2 & 0 & 0 & 0 \\ 0 & 0 & 0 & 0.5 & 0 & 0 \\ 0 & 0 & 0 & 0 & 0.25 & 0 \\ 0 & 0 & 0 & 0 & 0 & 0.25 \end{bmatrix}$$

$$= \begin{bmatrix} 2 & 0.5 & 0.5 & 0 & 0 & 0 \\ 0.5 & 3 & 0.75 & 0 & 0 & 0 \\ 0.5 & 0.75 & 2 & 0 & 0 & 0 \\ 0 & 0 & 0 & 0.5 & 0 & 0 \\ 0 & 0 & 0 & 0 & 0.25 & 0 \\ 0 & 0 & 0 & 0 & 0 & 0.25 \end{bmatrix}$$

(b)

Using Matlab, we calculate the transvers if the stiffness matrix, compliance matrix D

$$D = C^{-1} = \begin{bmatrix} 0.5320 & -0.0756 & -0.0523 & 0 & 0 & 0 \\ -0.0756 & 0.3605 & -0.0581 & 0 & 0 & 0 \\ -0.0523 & -0.0581 & 0.2674 & 0 & 0 & 0 \\ 0 & 0 & 0 & 2 & 0 & 0 \\ 0 & 0 & 0 & 0 & 4 & 0 \\ 0 & 0 & 0 & 0 & 0 & 4 \end{bmatrix}$$

Notice that this is for engineering strain. If tensorial strain is used, the bottom-right quardrant shall be applied a multiplyer of 1/2.

(c)

There are not definite relationship between $D^1_{IK}\, D^2_{IJ}$and$C^1_{IK}\, C^2_{IJ}$

From the calculation above, we see that the ralationship between $C^1_{IK}\, C^2_{IJ}$and $C_{ijkl}$is not one to

one.

There are numerous sets of C^1_{IK} and C^2_{IJ} that can get the same C_{ijkl} as long as $C^1_{ii} + 2C^2_{ii}\,(i = 1, 2, 3)$

keeps the same value.

The same is for D^1_{IK} and D^2_{IJ}, their compositioncan be various and may not be determined uniquely.

However, we can still get the one way to obtain the general relation between $C^1_{IK}\, C^2_{IJ}$and$D^1_{IK}\, D^2_{IJ}$

Let

$$C^3 = \begin{bmatrix} C^1_{11} + C^2_{11}\times 2 & C^1_{12} & C^1_{13} \\ C^1_{21} & C^1_{22} + C^2_{22}\times 2 & C^1_{32} \\ C^1_{31} & C^1_{32} & C^1_{33} + C^2_{33}\times 2 \end{bmatrix}$$

$$D^3 = \begin{bmatrix} D^1_{11} + D^2_{11}\times 2 & D^1_{12} & D^1_{13} \\ D^1_{21} & D^1_{22} + D^2_{22}\times 2 & D^1_{32} \\ D^1_{31} & D^1_{32} & D^1_{33} + D^2_{33}\times 2 \end{bmatrix}$$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

$$C^4 = \begin{bmatrix} C_{23}^2 & & \\ & C_{13}^2 & \\ & & C_{12}^2 \end{bmatrix}$$

$$D^4 = \begin{bmatrix} D_{23}^2 & & \\ & D_{13}^2 & \\ & & D_{12}^2 \end{bmatrix}$$

Since CD = I

We have

$C^3 D^3 = I$

$C^4 D^4 = I$

So when $C_{IK}^1 C_{IJ}^2$ is determined,we can calculate get $D^3 D^4$,based on D^4 we get

$$\begin{cases} D_{23}^2 = D_{32}^2 = (C_{23}^2)^{-1} \\ D_{13}^2 = D_{31}^2 = (C_{13}^2)^{-1} \\ D_{12}^2 = D_{21}^2 = (C_{12}^2)^{-1} \end{cases}$$

Then $D_{11}^2 D_{22}^2 D_{33}^2$, could be chosen to be any value

From D^3we get

$D_{ij}^1 = D_{ij}^3 (i \neq j)$

And

$$\begin{cases} D_{11}^1 = D_{11}^3 - 2 \times D_{11}^2 \\ D_{22}^1 = D_{22}^3 - 2 \times D_{22}^2 \\ D_{33}^1 = D_{33}^3 - 2 \times D_{33}^2 \end{cases}$$

So by now we solve the problem. If we have the value of $C_{IK}^1 C_{IJ}^2$, we can get the according value for

$D_{IK}^1 D_{IJ}^2$,but they are not uniquely determined. From the above derivation, we can also provide an analytical form for the case of tensorial strains.

6. Prove the following identities

$$\nabla \times (\nabla \phi) = \mathbf{0},$$
$$\nabla \cdot (\nabla \times \mathbf{a}) = 0,$$
$$\nabla \times (\nabla \times \mathbf{a}) = \nabla (\nabla \cdot \mathbf{a}) - \nabla^2 \mathbf{a}$$

where ϕ is a scalar field and $\mathbf{a}$ a vector field.

Proof:

(1) $\nabla \times (\nabla \phi) = \varepsilon_{ijk} \phi_{,kj} = -\varepsilon_{ikj} \phi_{,kj} = -\varepsilon_{ijk} \phi_{,kj} = 0$(Switch j,k in the last two formulas)

(2) $\nabla \cdot (\nabla \times \mathbf{a}) = (\varepsilon_{ijk} a_{j,k})_{,i} = \varepsilon_{ijk} a_{j,ki} = -\varepsilon_{kji} a_{j,ik} = -\varepsilon_{ijk} a_{j,ki} = 0$(Switch i, k in the last two formulas)

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

(3)$\nabla \times (\nabla \times \mathbf{a})$= $\varepsilon_{ijk}(\varepsilon_{kmn}a_{n,m})_{,j} = (\varepsilon_{ijk}\varepsilon_{kmn})a_{n,mj}$

$= (\delta_{im}\delta_{jn} - \delta_{in}\delta_{jm})a_{n,mj} = a_{j,ij} - a_{i,jj} = \nabla(\nabla \cdot \mathbf{a}) - \nabla^2\mathbf{a}$

7. Given a scalar field in a 3-dimensional infinite domain as $\psi = |\mathbf{x} - \mathbf{x}^0|$, which is a distance from $\mathbf{x}$ to a known point $\mathbf{x}^0$, derive $\nabla\nabla\psi$, which is a second rank tensor. Similarly, for $\phi = 1/|\mathbf{x} - \mathbf{x}^0|$, derive $\nabla\nabla\phi$.

Answer:

Let $r = \left|x - x^0\right|^2$

First we get

$\nabla\psi = \frac{d\psi}{dr}\frac{dr}{dx_i} = \frac{1}{2\left|x - x^0\right|} \cdot 2(x_i - x_i^0)$

$= \frac{(x_i - x_i^0)}{\left|x - x^0\right|}$

$\nabla\nabla\psi = -\frac{1}{2\left|x - x^0\right|^3}(x_i - x_i^0) \cdot 2(x_j - x_j^0) + \frac{\delta_{ij}}{\left|x - x^0\right|}$

$= \frac{-(x_i - x_i^0)(x_j - x_j^0) + \delta_{ij}\left|x - x^0\right|^2}{\left|x - x^0\right|^3}$

For $\phi = \frac{1}{\left|x - x^0\right|}$

$\nabla\psi = \frac{d\psi}{dr}\frac{dr}{dx_i} = -\frac{1}{2\left|x - x^0\right|} \cdot 2(x_i - x_i^0)$

$= \frac{-(x_i - x_i^0)}{\left|x - x^0\right|^3}$

$\nabla\nabla\psi = \frac{3}{2\left|x - x^0\right|^5}(x_i - x_i^0) \cdot 2(x_j - x_j^0) + \frac{\delta_{ij}}{\left|x - x^0\right|^3}$

$= \frac{3(x_i - x_i^0)(x_j - x_j^0) - \delta_{ij}\left|x - x^0\right|^2}{\left|x - x^0\right|^5}$

8. Given a vector field $\mathbf{a} = \mathbf{x}$ in a spherical domain Ω: $x_1^2 + x_2^2 + x_3^2 \leq 1$, use the Helmholtz's decomposition to write $\mathbf{a} = \nabla\varphi + \nabla \times \mathbf{b}$ in terms of a scalar potential and a vector potential $\mathbf{b}$. Find the specific form of φ and $\mathbf{b}$ in terms of x_i.

Answer:

From the textbook, we have

$a(x) = \nabla^2 u(x) = \nabla(\nabla \cdot u(x)) - \nabla \times (\nabla \times u(x))$

We choose

$\varphi = \nabla \cdot u(x)$

$b = -\nabla \times u(x)$

Then we can get

$a(x) = \nabla^2 u(x) = \nabla\varphi + \nabla \times b$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

So now we caculate $u(x)$

$\nabla^2 u(x) = a(x)$=x

We can get

$$u(x) = \left(\frac{x_1^3}{6} + x_1 f_1(x_2, x_3) + g_1(x_2, x_3), \frac{x_2^3}{6} + x_2 f_2(x_1, x_3) + g_2(x_1, x_3), \frac{x_3^3}{6} + x_3 f_3(x_1, x_2) + g_3(x_1, x_2)\right)$$

Here $f_1(x_2, x_3)$and $g_1(x_2, x_3)$are any functions

$$\varphi = \nabla \cdot u(x) = \frac{x_1^2}{2} + f_1(x_2, x_3) + \frac{x_2^2}{2} + f_2(x_1, x_3) + \frac{x_3^2}{2} + f_3(x_1, x_2)$$

$$b = -\nabla \times u(\mathbf{x}) = -\begin{vmatrix} \frac{\partial}{\partial x_1} & \frac{\partial}{\partial x_2} & \frac{\partial}{\partial x_3} \\ u_1(\mathbf{x}) & u_2(\mathbf{x}) & u_3(\mathbf{x}) \\ i & j & k \end{vmatrix}$$

$$= \begin{bmatrix} -\left(x_3 \frac{\partial f_3(x_1,x_2)}{\partial x_2} + \frac{\partial g_3(x_1,x_2)}{\partial x_2} - x_2 \frac{\partial f_2(x_1,x_3)}{\partial x_3} - \frac{\partial g_2(x_1,x_3)}{\partial x_3}\right) \\ x_2 \frac{\partial f_1(x_2,x_3)}{\partial x_3} + \frac{\partial g_1(x_2,x_3)}{\partial x_3} - x_3 \frac{\partial f_3(x_1,x_2)}{\partial x_1} - \frac{\partial g_3(x_1,x_2)}{\partial x_1} \\ x_2 \frac{\partial f_2(x_1,x_3)}{\partial x_1} + \frac{\partial g_2(x_1,x_3)}{\partial x_1} - x_1 \frac{\partial f_1(x_2,x_3)}{\partial x_2} - \frac{\partial g_1(x_2,x_3)}{\partial x_2} \end{bmatrix}$$

9. Consider a scalar field $\varphi = x_1^2 + x_2^2 + x_3^2$ in a spherical domain : $x_1^2 + x_2^2 + x_3^2 \leq 1$. Confirm the following equations:

$$\int_\Omega \nabla \varphi dV = \int_{\partial\Omega} \mathbf{n} \varphi dS$$

$$\int_\Omega \nabla^2 \varphi dV = \int_{\partial\Omega} \mathbf{n}.\nabla \varphi dS$$

Answer:

(1)

For the left hand side

$\int \nabla \varphi dV = \int 2x_i dV$

$=\overset{[}{r}=0]r=1\int \overset{[}{\theta}=0]\theta=\pi\int \overset{[}{\alpha}=0]\alpha=2\pi\int (2r\sin\theta\cos a) r^2\sin\theta dr d\theta d\alpha \mathbf{i}$

$+\overset{[}{r}=0]r=1\int \overset{[}{\theta}=0]\theta=\pi\int \overset{[}{\alpha}=0]\alpha=2\pi\int (2r\sin\theta\sin a) r^2\sin\theta dr d\theta d\alpha \mathbf{j}$

$+\overset{[}{r}=0]r=1\int \overset{[}{\theta}=0]\theta=\pi\int \overset{[}{\alpha}=0]\alpha=2\pi\int (2r\cos\theta) r^2\sin\theta dr d\theta d\alpha \mathbf{k}$

=0+0+0=0

For the right hand side

$\int_\partial \mathbf{n}\varphi dV$

$=\overset{[}{\theta}=0]\theta=\pi\int \overset{[}{\alpha}=0]\alpha=2\pi\int (\sin\theta\cos a)\sin\theta d\theta d\alpha \mathbf{i}$

$+\overset{[}{\theta}=0]\theta=\pi\int \overset{[}{\alpha}=0]\alpha=2\pi\int (\sin\theta\sin a)\sin\theta d\theta d\alpha \mathbf{j}$

$+\overset{[}{\theta}=0]\theta=\pi\int \overset{[}{\alpha}=0]\alpha=2\pi\int (\sin\theta\cos a) r^2\sin\theta d\theta d\alpha \mathbf{k}$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

=0+0+0=0

They are equal

(2)

For the left hand side

$\int_\Omega \nabla^2 \varphi dV = \int_\Omega 6dV = 8\pi$

while

$\int_{\partial\Omega} \mathbf{n}.\nabla\varphi dS = \overset{[}{\theta} = 0]\theta = \pi \int \overset{[}{\alpha} = 0]\alpha = 2\pi \int 2\left[\sin^2\theta\left(\cos^2\alpha + \sin^2\alpha\right) + \cos^2\theta\right]\sin\theta d\theta d\alpha$

$= \overset{[}{\theta} = 0]\theta = \pi \int \overset{[}{\alpha} = 0]\alpha = 2\pi \int 2\sin\theta d\theta d\alpha$

$=8\pi$

They are equal.

10. Prove $G(\mathbf{x}, \mathbf{x}') = ln\frac{1}{|\mathbf{x}-\mathbf{x}'|}$ is the Green's function for the 2-dimensional Laplace equation.

Proof:

$G(\mathbf{x}, \mathbf{x}') = ln\frac{1}{|\mathbf{x}-\mathbf{x}'|}$

When x$\neq x$'

$\nabla^2 G(\mathbf{x}, \mathbf{x}') = \frac{\partial}{\partial x_i}\left\{|x - x'|\frac{\partial}{\partial x_i}\left[(x - x')^2\right]^{-\frac{1}{2}}\right\}$

$= \frac{\partial}{\partial x_i}\left\{|x - x'|\left(-\frac{1}{2}\right)\left[(x - x')^2\right]^{-\frac{3}{2}} 2\left(x_i - x_i'\right)\right\}$

$= -\frac{\partial}{\partial x_i}\frac{\left(x_i - x_i'\right)^2}{\left|x - x'\right|^2}$

$= -\frac{2}{|x-x'|^2} - \left\{-1\left[(x - x')^2\right]^{-2} 2\left(x_i - x_i'\right)^2\right\}$

$= -\frac{2}{|x-x'|^2} + \frac{2\left(x_i - x_i'\right)^2}{|x-x'|^4}$

$= -\frac{2}{|x-x'|^2} + \frac{2|x-x'|^2}{|x-x'|^4}$

$=0$

Here since it's two dimensional, $\frac{\partial}{\partial x_i}x_i = 2$

When x=x' , this point is nondifferentiable

From above we know that

$\frac{\partial G(x,x')}{\partial x_i} = -\frac{\left(x_i - x_i'\right)}{\left|x-x'\right|^2}$

If we take derivative with x', then it is

$\frac{\partial G(x,x')}{\partial x_i'} = -\frac{\left(x_i - x_i'\right)}{\left|x-x'\right|^2}$

Using Guass equation

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

$\int_\Omega \nabla^2 G(x,x')\,dx' = \int_{\partial\Omega} \nabla G(x,x')\,\mathbf{n}dx' = \int_{\partial\Omega} \frac{(x_i - x_i')}{|x-x'|^2} n_i dx'$

Since $\nabla^2 G(x,x') = 0$ everywhere except x=x', we can choose any $\partial\Omega$. Just choose it to be a circle

radius of one and centered at x,

Then

$\int_\Omega \nabla^2 G(x,x')\,dx'$

$= \int_{\partial\Omega} \frac{(x_i - x_i')}{|x-x'|^2} n_i dx'$

$= \overset{[}{\theta} = 0]\theta = 2\pi \int \overset{[}{\theta} = 0]\theta = \pi \int -\left(\sin^2\theta\cos^2\varphi + \sin^2\theta\sin^2\varphi + \cos^2\theta\right)\sin\theta d\theta d\varphi$

$= \overset{[}{\theta} = 0]\theta = 2\pi \int \overset{[}{\theta} = 0]\theta = \pi \int -1\sin\theta d\theta d\varphi$

= -2π

So it is Green function in two dimension

And it is better written in the form of

$G(\mathbf{x},\mathbf{x}') = -\frac{1}{2\pi} ln \frac{1}{|\mathbf{x}-\mathbf{x}'|}$

11. Derive the Green's function for a cantilever beam bending.

Answer:

For the cantilever, using the same procedure in class, we have

$EI \cdot G(x-x') = \frac{(x-x')^3}{6} H(x-x') + \frac{C_1}{6}x^3 + \frac{C_2}{2}x^2 + C_3 x + C_4$

There is no displacement and tilt angle at the starting point x=0,

And the moment caused by this point force is x' at x=0 and 0 at x=L

So boundary condition is

$$\begin{cases} G(x-x') = 0\,(x=0) \\ G'(x-x') = 0\,(x=0) \\ G''(x-x') = x'\,(x=0) \\ G''(x-x') = 0\,(x=L) \end{cases}$$

From these we can determine

$$\begin{cases} C_1 = -1 \\ C_2 = x' \\ C_3 = 0 \\ C_4 = 0 \end{cases}$$

So the Green function is

$G(x-x') = \frac{1}{EI}\left[\frac{(x-x')^3}{6} H(x-x') + \frac{1}{6}x^3 + \frac{x'}{2}x^2\right]$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

The beam's deflection shape function can be written as

$w = \int_{\Omega} G(x, x') q(x') dx'$‘

12. Write the 6 equations implied by compatibility condition for strains $\nabla \times \epsilon \times \nabla = \mathbf{0}$.

Answer:

$\nabla \times \epsilon \times \nabla = \left(\varepsilon_{kim} \frac{\partial \varepsilon_{ij}}{\partial x_k}\right) \varepsilon_{jln} \frac{\partial}{\partial x_1} = (\varepsilon_{kim}\varepsilon_{jnl}) \partial \varepsilon_{ij,kl} = \mathbf{0}$

when$(m = 1, n = 1)$

$(\varepsilon_{ki1}\varepsilon_{j1l}) \partial \varepsilon_{ij,kl} = (\varepsilon_{231}\varepsilon_{213}) \partial \varepsilon_{32,23} (k = 2, i = 3, j = 2, l = 3)$

$+(\varepsilon_{231}\varepsilon_{312}) \partial \varepsilon_{33,22} (k = 2, i = 3, j = 3, l = 2)$

$+(\varepsilon_{321}\varepsilon_{213}) \partial \varepsilon_{22.33} (k = 3, i = 2, j = 2, l = 3)$

$+(\varepsilon_{321}\varepsilon_{312}) \partial \varepsilon_{23,32} (k = 3, i = 2, j = 3, l = 2)$

$= -\varepsilon_{32,23} + \varepsilon_{33,22} + \varepsilon_{22,33} - \varepsilon_{23,32}$

$= 0$

So similar when $(m = 2, n = 2)$

We get

$-\varepsilon_{21,12} + \varepsilon_{22,11} + \varepsilon_{11,22} - \varepsilon_{12,21} = 0$

When $(m = 3, n = 3)$

$-\varepsilon_{13,31} + \varepsilon_{11.33} + \varepsilon_{33,11} - \varepsilon_{31,13} = 0$

$(m = 1, n = 2)$

$(\varepsilon_{ki1}\varepsilon_{j2l}) \partial \varepsilon_{ij,kl} = (\varepsilon_{231}\varepsilon_{213}) \partial \varepsilon_{31,23} (k = 2, i = 3, j = 1, l = 3)$

$+(\varepsilon_{231}\varepsilon_{321}) \partial \varepsilon_{33,21} (k = 2, i = 3, j = 3, l = 1)$

$+(\varepsilon_{321}\varepsilon_{123}) \partial \varepsilon_{21.33} (k = 3, i = 2, j = 1, l = 3)$

$+(\varepsilon_{321}\varepsilon_{321}) \partial \varepsilon_{23,31} (k = 3, i = 2, j = 3, l = 1)$

When $(m = 3, n = 1)$

$\varepsilon_{23,12} + \varepsilon_{22.33} + \varepsilon_{13,22} - \varepsilon_{12.23} = 0$

In conclude the six equations we get are:

$$\begin{cases} \varepsilon_{33,22} + \varepsilon_{22.33} - 2\varepsilon_{23,32} = 0 \\ \varepsilon_{22,11} + \varepsilon_{11,22} - 2\varepsilon_{12,21} = 0 \\ \varepsilon_{11.33} + \varepsilon_{33,11} - 2\varepsilon_{31,13} = 0 \\ \varepsilon_{31,23} - \varepsilon_{33,21} - \varepsilon_{21,33} + \varepsilon_{23,31} = 0 \\ \varepsilon_{12,31} - \varepsilon_{11,32} - \varepsilon_{32,11} + \varepsilon_{23,12} = 0 \\ \varepsilon_{12,31} - \varepsilon_{11,32} - \varepsilon_{32,11} + \varepsilon_{31,12} = 0 \end{cases}$$

13. Solve the boundary value problem: For a solid elastic ball fully boned by an outer layer, the radius of the ball and outer surface radii are written as $R_i < R_o$, respectively. The

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Young's moduli and Poisson's ratios of the ball and outer layer are respectively written as E_i and v_i and E_o and v_o. When a pressure P is applied on the outer surface, derive the displacement distribution along the radial direction in two materials.

Answer:

For strain condition

$\varepsilon_{rr} = u_{r,r}$

$\varepsilon_{\theta\theta} = \varepsilon_{\varphi\varphi} = \frac{u_r}{r}$

Equilibrium equation

$\sigma_{rr,r} + \frac{2\sigma_{rr} - \sigma_{\theta\theta} - \sigma_{\varphi\varphi}}{r} = 0$

Constitutive equation

$\sigma_{rr} = \lambda\left(\varepsilon_{rr} + \varepsilon_{\theta\theta} + \varepsilon_{\varphi\varphi}\right) + 2\mu\varepsilon_{rr} = (2\mu + \lambda)\, u_{r,r} + 2\lambda\frac{u_r}{r}$

Here to be convenient ,we use λ μ to replace E v

The relationship is

$\lambda = \frac{Ev}{(1+v)(1-2v)}$

$\mu = \frac{E}{2(1+v)}$

According to the textbook,the displacement of this kind of problem could be written as

$u_r = C_1 r + \frac{C_2}{r^2}$ Out layer

$u_r^* = C_1^* r + \frac{C_2^*}{r^2}$ inside sphere

Assure the stress between the two different materials is $\sigma_{rr}|_{r=Ri} = P^*$

We have two separate problems

$u_r = C_1 r + \frac{C_2}{r^2} \quad Ri \le r \le Ro$

$$\begin{cases} \sigma_{rr}|_{r=Ro} = -P \\ \sigma_{rr}|_{r=Ri} = -P^* \end{cases} \quad (1)$$

$u_r^* = C_1^* r + \frac{C_2^*}{r^2} \quad r \le Ri$

$$\begin{cases} u_r^*|_{r=0} = 0 \\ \sigma_{rr}^*|_{r=Ri} = P^* \end{cases} \quad (2)$$

$u_r = u_r^*|_{r=Ri}$

For the first boundary value problem, we get

$C_1 = \frac{R_o^3 P^* - (2R_o^3 - R_i^3)P}{(2\mu_o + 3\lambda_o)(R_0^3 - R_i^3)}$

$C_2 = \frac{R_o^3 R_i^3 (P* - P)}{4\mu_o (R_0^3 - R_i^3)}$

$u_r = \frac{R_i^3 P^* - (2R_o^3 - R_i^3)P}{(2\mu_o + 3\lambda_o)(R_0^3 - R_i^3)} r + \frac{R_o^3 R_i^3 (P* - P)}{4\mu_o (R_0^3 - R_i^3)} \frac{1}{r^2}$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

For the second boundary condition,

At r=0 there is no displacement, so we can get $C_2* = \frac{P*}{2\mu_i+3\lambda_i}$

$u_r* = \frac{P*}{2\mu+3\lambda}r$

Then the problem is to decide P*

The displacement of the two material at the interface must be equal

$u_r = u_r^*|_{r=Ri}$

So we have

$\frac{R_i^3P^*-(2R_o^3-R_i^3)P}{(2\mu_o+3\lambda_o)(R_0^3-R_i^3)}R_i + \frac{R_o^3R_i^3(P*-P)}{4\mu_o(R_0^3-R_i^3)}\frac{1}{R_I^2} = \frac{P*}{2\mu+3\lambda}R_i$

From this we get

$$P^* = \left[\left(\frac{(2R_o^3-R_i^3)R_i}{(2\mu_o+3\lambda_o)(R_0^3-R_i^3)} + \frac{R_o^3R_i}{4\mu_o(R_0^3-R_i^3)}\right) / \left(\frac{R_i^4}{(2\mu_o+3\lambda_o)(R_0^3-R_i^3)} + \frac{R_o^3R_i}{4\mu_o(R_0^3-R_i^3)} - \frac{R_i}{2\mu_i+3\lambda_i}\right)\right] P$$

In conclude ,the solution of this problem is

For the inner solid elastic ball,

$u_r* = \frac{P*}{2\mu+3\lambda}r$

For the outer layer

$u_r = \frac{R_i^3P^*-(2R_o^3-R_i^3)P}{(2\mu_o+3\lambda_o)(R_0^3-R_i^3)}r + \frac{R_o^3R_i^3(P*-P)}{4\mu_o(R_0^3-R_i^3)}\frac{1}{r^2}$

Here

$$P^* = \left[\left(\frac{(2R_o^3-R_i^3)R_i}{(2\mu_o+3\lambda_o)(R_0^3-R_i^3)} + \frac{R_o^3R_i}{4\mu_o(R_0^3-R_i^3)}\right) / \left(\frac{R_i^4}{(2\mu_o+3\lambda_o)(R_0^3-R_i^3)} + \frac{R_o^3R_i}{4\mu_o(R_0^3-R_i^3)} - \frac{R_i}{2\mu_i+3\lambda_i}\right)\right] P$$

$\lambda = \frac{Ev}{(1+v)(1-2v)}$

$\mu = \frac{E}{2(1+v)}$.

14. The stress tensor in a semi-infinite domain $x_3 > 0$ is given by $\sigma_{ij} = (\alpha x_i x_j x_3)/|x|^5$, where $|x| = (x_i x_i)^{1/2}$ and α is a constant. Determine whether there are any body forces in the domain using the equilibrium equation.

Answer:

The equilibrium equation is

$\sigma_{ij,j} + b_i = 0$

From the expression of stress we can get

$$\sigma_{ij,j} = \frac{(\alpha\delta_{ij}x_jx_3)}{|x|^5} + \frac{(\alpha\delta_{jj}x_ix_3)}{|x|^5} + \frac{(\alpha x_ix_jx_3)}{|x|^7}\left(\frac{-5}{2}\right)(2x_j)$$

$$= \frac{(\alpha x_ix_3)}{|x|^5} + \frac{(3\alpha x_ix_3)}{|x|^5} + \frac{(\alpha x_ix_3)}{|x|^5} - \frac{5\left(\alpha x_i|x|^2x_3\right)}{|x|^7}$$

$$= \frac{5\alpha x_ix_3}{|x|^5} - \frac{5\alpha x_ix_3}{|x|^5}$$

$=0$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

So

$b_i = 0 - 0 = 0$

Body force is zero.

15. In an infinite solid with material elastic constants μ and v, a concentrated force P = (0, 0, 1) is applied at the origin. Calculate the surface force distribution on the sphere with radius 1 and the center at the origin. Integrate it over the surface for the resultant surface force.

Answer:

First we use the formula in textbook

$$u_i = \frac{P}{16\pi\mu(1-v)}\left[(3-4v)\frac{\delta_{ij}}{\left|x-x'\right|} + \frac{\left(x_i-x_i'\right)\left(x_j-x_j'\right)}{\left|x-x'\right|^3}\right]P_j$$

In this case , we get

$$u_i = \frac{P}{16\pi\mu(1-v)}\left(\frac{x_1x_3}{|x|^3}, \frac{x_2x_3}{|x|^3}, \frac{3-4v}{|x|} + \frac{x_3^2}{|x|^3}\right)$$

Then we can calculate strain

$\varepsilon = \frac{1}{2}(\frac{\partial u_i}{\partial x_j} + \frac{\partial u_j}{\partial x_i})$

$$= \frac{P}{16\pi\mu(1-v)}\begin{bmatrix} \frac{\partial\left(\frac{x_1x_3}{|x|^3}\right)}{\partial x_1} & \frac{1}{2}\left[\frac{\partial\left(\frac{x_2x_3}{|x|^3}\right)}{\partial x_1} + \frac{\partial\left(\frac{x_1x_3}{|x|^3}\right)}{\partial x_2}\right] & \frac{1}{2}\left[\frac{\partial\left(\frac{3-4v}{|x|} + \frac{x_3^2}{|x|^3}\right)}{\partial x_1} + \frac{\partial\left(\frac{x_1x_3}{|x|^3}\right)}{\partial x_3}\right] \\ \frac{1}{2}\left[\frac{\partial\left(\frac{x_2x_3}{|x|^3}\right)}{\partial x_1} + \frac{\partial\left(\frac{x_1x_3}{|x|^3}\right)}{\partial x_2}\right] & \frac{\partial\left(\frac{x_2x_3}{|x|^3}\right)}{\partial x_2} & \frac{1}{2}\left[\frac{\partial\left(\frac{3-4v}{|x|}\frac{x_3^2}{|x|^3}\right)}{\partial x_2} + \frac{\partial\left(\frac{x_2x_3}{|x|^3}\right)}{\partial x_3}\right] \\ \frac{1}{2}\left[\frac{\partial\left(\frac{3-4v}{|x|} + \frac{x_3^2}{|x|^3}\right)}{\partial x_1} + \frac{\partial\left(\frac{x_1x_3}{|x|^3}\right)}{\partial x_3}\right] & \frac{1}{2}\left[\frac{\partial\left(\frac{3-4v}{|x|}\frac{x_3^2}{|x|^3}\right)}{\partial x_2} + \frac{\partial\left(\frac{x_2x_3}{|x|^3}\right)}{\partial x_3}\right] & \frac{\partial\left(\frac{3-4v}{|x|}\frac{x_3^2}{|x|^3}\right)}{\partial x_3} \end{bmatrix}$$

$$= \frac{P}{16\pi\mu(1-v)}\begin{bmatrix} \frac{x_3}{|x|^3} - \frac{3x_1^2x_3}{|x|^5} & -\frac{3x_1^2x_2x_3}{|x|^5} & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_1 - \right. \\ -\frac{3x_1^2x_2x_3}{|x|^5} & \frac{x_3}{|x|^3} - \frac{3x_2^2x_3}{|x|^5} & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_2 - \right. \\ \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_1 - \frac{3x_3^2}{|x|^5}x_1 + \frac{x_1}{|x|^3} - \frac{3x_1x_3^2}{|x|^5}\right) & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_2 - \frac{3x_3^2}{|x|^5}x_2 + \frac{x_2}{|x|^3} - \frac{3x_2x_3^2}{|x|^5}\right) & -\frac{3-4v}{|x|^3}x_3 \end{bmatrix}$$

According to the elasticity constitutive equation using μ, v,the ralation between stress and strain is

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

$$\sigma_{ij} = \frac{2\mu v}{1-2v}\varepsilon_{kk}\delta_{ij} + 2\mu\varepsilon_{ij}$$

$$\varepsilon_{kk} = \frac{P}{16\pi\mu(1-v)}\left(\frac{4x_3}{|x|^3} - \frac{3(x_1^2+x_2^2+x_3^2)x_3}{|x|^5} - \frac{3-4v}{|x|^3}x_3\right)$$

$$= \frac{P}{16\pi\mu(1-v)}\left(\frac{x_3}{|x|^3} - \frac{3-4v}{|x|^3}x_3\right)$$

$$= -\frac{P}{16\pi\mu(1-v)}\left(\frac{2-4v}{|x|^3}x_3\right)$$

$$\sigma_{ij} = \frac{2\mu v}{1-2v}\varepsilon_{kk}\delta_{ij} + 2\mu\varepsilon_{ij}$$

$$= \frac{2\mu v}{1-2v}\frac{P}{16\pi\mu(1-v)}\begin{bmatrix} -\frac{2-4v}{|x|^3}x_3 & 0 & 0 \\ 0 & -\frac{2-4v}{|x|^3}x_3 & 0 \\ 0 & 0 & -\frac{2-4v}{|x|^3}x_3 \end{bmatrix}$$

$$+2\mu\frac{P}{16\pi\mu(1-v)}\begin{bmatrix} \frac{x_3}{|x|^3} - \frac{3x_1^2x_3}{|x|^5} & -\frac{3x_1x_2x_3}{|x|^5} & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_1 - \right. \\ -\frac{3x_1x_2x_3}{|x|^5} & \frac{x_3}{|x|^3} - \frac{3x_2^2x_3}{|x|^5} & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_2 - \right. \\ \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_1 - \frac{3x_3^2}{|x|^5}x_1 + \frac{x_1}{|x|^3} - \frac{3x_1x_3^2}{|x|^5}\right) & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_2 - \frac{3x_3^2}{|x|^5}x_2 + \frac{x_2}{|x|^3} - \frac{3x_2x_3^2}{|x|^5}\right) & -\frac{3-4v}{|x|^3} \end{bmatrix}$$

$$= \frac{vP}{4\pi(1-v)}\begin{bmatrix} -\frac{x_3}{|x|^3} & 0 & 0 \\ 0 & -\frac{x_3}{|x|^3} & 0 \\ 0 & 0 & -\frac{x_3}{|x|^3} \end{bmatrix}$$

$$+\frac{P}{8\pi(1-v)}\begin{bmatrix} \frac{x_3}{|x|^3} - \frac{3x_1^2x_3}{|x|^5} & -\frac{3x_1x_2x_3}{|x|^5} & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_1 - \right. \\ -\frac{3x_1x_2x_3}{|x|^5} & \frac{x_3}{|x|^3} - \frac{3x_2^2x_3}{|x|^5} & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_2 - \right. \\ \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_1 - \frac{3x_3^2}{|x|^5}x_1 + \frac{x_1}{|x|^3} - \frac{3x_1x_3^2}{|x|^5}\right) & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_2 - \frac{3x_3^2}{|x|^5}x_2 + \frac{x_2}{|x|^3} - \frac{3x_2x_3^2}{|x|^5}\right) & -\frac{3-4v}{|x|^3}x_3 - \end{bmatrix}$$

$$f_i = \sigma_{ij}n_j \; (n_j = (x_1, x_2, x_3))$$

$$= \frac{vP}{4\pi(1-v)}\begin{bmatrix} -\frac{x_3}{|x|^3} & 0 & 0 \\ 0 & -\frac{x_3}{|x|^3} & 0 \\ 0 & 0 & -\frac{x_3}{|x|^3} \end{bmatrix}\begin{bmatrix} x_1 \\ x_2 \\ x_3 \end{bmatrix}$$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

$$+\frac{P}{8\pi(1-v)}\begin{bmatrix} \frac{x_3}{|x|^3}-\frac{3x_1^2x_3}{|x|^5} & -\frac{3x_1x_2x_3}{|x|^5} & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_1-\frac{3x}{|x| \\ -\frac{3x_1x_2x_3}{|x|^5} & \frac{x_3}{|x|^3}-\frac{3x_2^2x_3}{|x|^5} & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_2-\frac{3x}{|x| \\ \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_1-\frac{3x_3^2}{|x|^5}x_1+\frac{x_1}{|x|^3}-\frac{3x_1x_3^2}{|x|^5}\right) & \frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_2-\frac{3x_3^2}{|x|^5}x_2+\frac{x_2}{|x|^3}-\frac{3x_2x_3^2}{|x|^5}\right) & -\frac{3-4v}{|x|^3}x_3- \end{bmatrix}$$

$$=\frac{vP}{4\pi(1-v)}\begin{bmatrix} -\frac{x_1x_3}{|x|^3} \\ -\frac{x_2x_3}{|x|^3} \\ -\frac{x_3^2}{|x|^3} \end{bmatrix}+\frac{P}{8\pi(1-v)}\begin{bmatrix} \frac{x_1x_3}{|x|^3}-\frac{3x_1^3x_3}{|x|^5}-\frac{3x_1x_2^2x_3}{|x|^5}+\frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_1x_3-\frac{3x_3^3}{|x|^5}x_1+\frac{x_1x_3}{|x|^3}-\frac{3x_1x_3^4}{|x|^5}\right) \\ \frac{x_2x_3}{|x|^3}-\frac{3x_2^3x_3}{|x|^5}-\frac{3x_1^2x_2x_3}{|x|^5}+\frac{1}{2}\left(-\frac{3-4v}{|x|^3}x_2x_3-\frac{3x_3^3}{|x|^5}x_2+\frac{x_2x_3}{|x|^3}-\frac{3x_2x_3^4}{|x|^5}\right) \\ \frac{1}{2}\left(-\frac{3-4v}{|x|}-\frac{3x_3^2}{|x|^3}+\frac{1}{|x|}-\frac{3x_3^2}{|x|^3}\right)-\frac{1}{2}\frac{3-4v}{|x|^3}x_3^2+\frac{3x_3^2}{2|x|^3} \end{bmatrix}$$

$$=\frac{vP}{4\pi(1-v)}\begin{bmatrix} -\frac{x_1x_3}{|x|^3} \\ -\frac{x_2x_3}{|x|^3} \\ -\frac{x_3^2}{|x|^3} \end{bmatrix}+\frac{P}{8\pi(1-v)}\begin{bmatrix} -\frac{(3-2v)x_1x_3}{|x|^3} \\ -\frac{(3-2v)x_2x_3}{|x|^3} \\ -\frac{1-2v}{|x|}-\frac{3-2v}{|x|^3}x_3^2 \end{bmatrix}$$

$$=\frac{P}{8\pi(1-v)}\begin{bmatrix} -\frac{2vx_1x_3}{|x|^3}-\frac{(3-2v)x_1x_3}{|x|^3} \\ -\frac{2vx_2x_3}{|x|^3}-\frac{(3-2v)x_2x_3}{|x|^3} \\ -\frac{2vx_3^2}{|x|^3}-\frac{1-2v}{|x|}-\frac{3-2v}{|x|^3}x_3^2 \end{bmatrix}$$

$$=\frac{P}{8\pi(1-v)}\begin{bmatrix} -\frac{3x_1x_3}{|x|^3} \\ -\frac{3x_2x_3}{|x|^3} \\ -\frac{1-2v}{|x|}-\frac{3x_3^2}{|x|^3} \end{bmatrix}$$

For the resultan surface force , they are

$f=\int_{\partial\Omega} f_i$

$$=\int_{\partial\Omega}\frac{P}{8\pi(1-v)}\begin{bmatrix} \frac{3x_1x_3}{|x|^3} \\ \frac{3x_2x_3}{|x|^3} \\ -\frac{1-2v}{|x|}+\frac{3x_3^2}{|x|^3} \end{bmatrix}_i$$

$$=\frac{P}{8\pi(1-v)}\begin{bmatrix} 0 \\ 0 \\ -(1-2v)\overset{[}{a}=0]2\pi\int\overset{[}{\theta}=0]\theta=\pi\int\sin\theta d\theta da-3\overset{[}{a}=0]2\pi\int\overset{[}{\theta}=0]\theta=\pi\int\cos^2\theta\sin\theta d\theta da \end{bmatrix}$$

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

$$= \frac{P}{8\pi(1-v)} \begin{bmatrix} 0 \\ 0 \\ -(1-2v)\,2\pi\left[-\cos\theta\right]_0^{\pi} - 3\cdot 2\pi\left[\frac{-\cos^3\theta}{3}\right]_0^{\pi} \end{bmatrix}$$

$$= \frac{P}{8\pi(1-v)} \begin{bmatrix} 0 \\ 0 \\ -(1-2v)\,4\pi - 4\pi \end{bmatrix}$$

$$= \begin{bmatrix} 0 \\ 0 \\ -P \end{bmatrix}$$

The first two items are zero because symmetry.

The result is correct in which the force around the sphere balance the concentrated force.

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Courtesy of CRC Press/Taylor & Francis Group

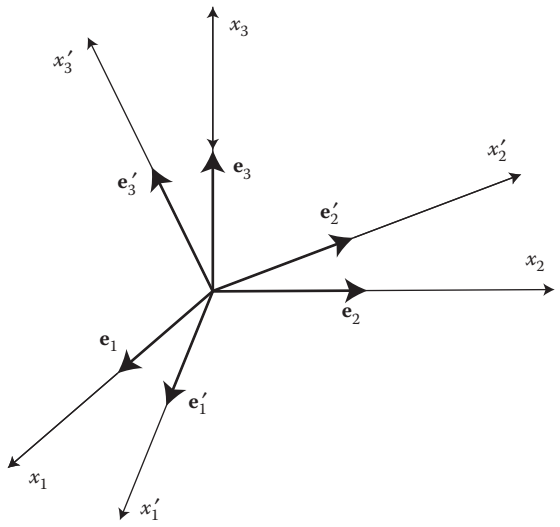


Figure 2.1 Three-dimensional Cartesian coordinate and coordinate rotation.

K24880˙C002

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Courtesy of CRC Press/Taylor & Francis Group

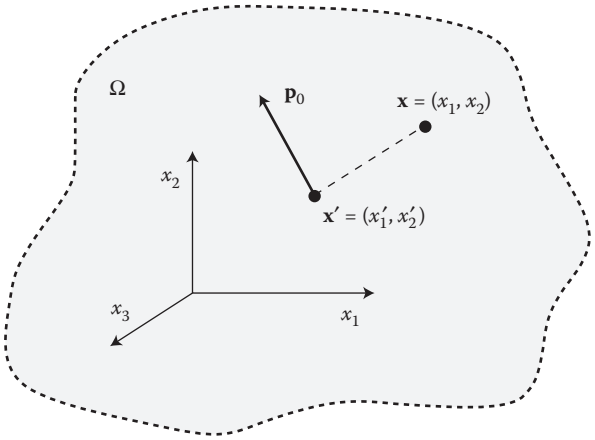


Figure 2.2 Green's function.

K24880˙C002

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Courtesy of CRC Press/Taylor & Francis Group

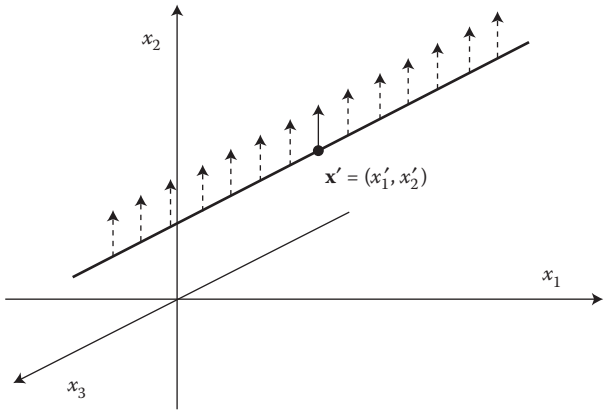


Figure 2.3 Dimension reduction of Green's function.

K24880˙C002

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Courtesy of CRC Press/Taylor & Francis Group

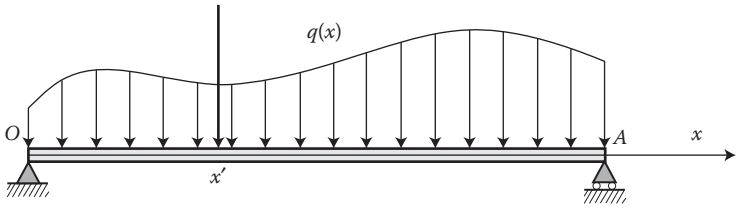


Figure 2.4 Straight beam under distribution loading.

K24880˙C002

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Courtesy of CRC Press/Taylor & Francis Group

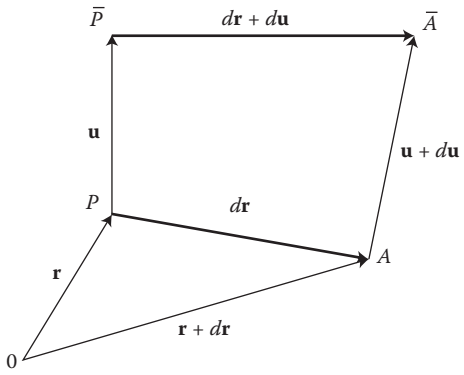


Figure 2.5 Deformation of an infinitesimal line element.

K24880˙C002

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Courtesy of CRC Press/Taylor & Francis Group

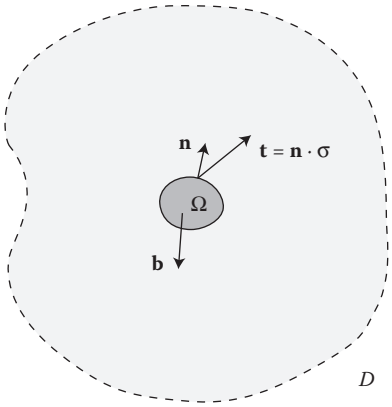


Figure 2.6 The equilibrium of an arbitrary domain.

K24880˙C002

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Courtesy of CRC Press/Taylor & Francis Group

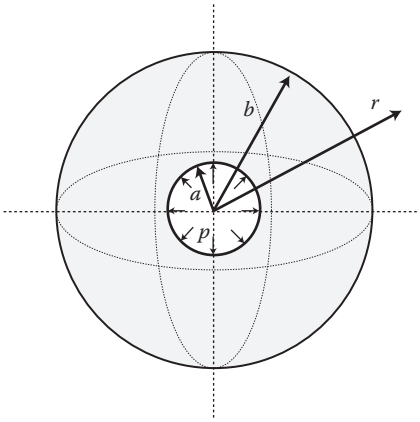


Figure 2.7 A ball subjected to a uniform inner pressure p.

K24880˙C002

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Courtesy of CRC Press/Taylor & Francis Group

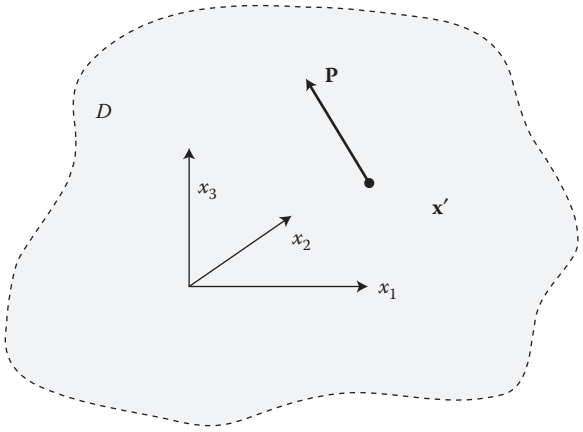


Figure 2.8 Concentrated force acting on an infinite domain.

K24880˙C002

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual

Courtesy of CRC Press/Taylor & Francis Group

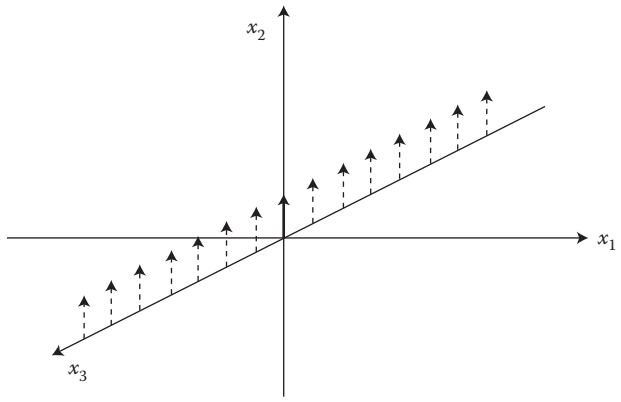


Figure 2.9 Dimension reduction of Kelvin's solution.

K24880˙C002

Introduction to the Micromechanics of Composite Materials 1st edition Yin Solutions Manual